

## 4.2. DISORDER DIFFUSE SCATTERING OF X-RAYS AND NEUTRONS

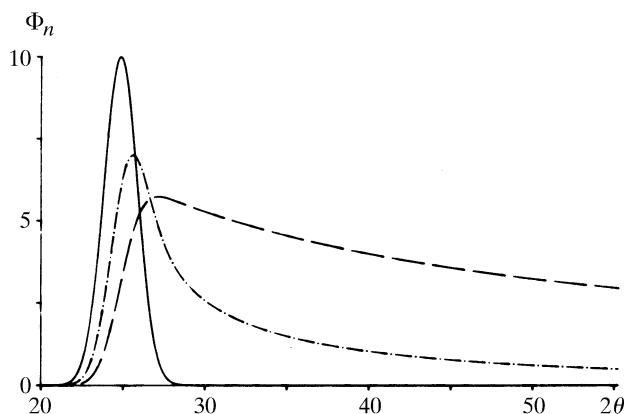


Fig. 4.2.8.2. Line profiles in powder diffraction for diffuse peaks (full line), continuous streaks (dot-dash lines) and continuous planes (broken lines). For explanation see text.

$P$  denotes a scaling factor that depends on the instrumental luminosity,  $T$  is the shortest distance to the origin of the reciprocal lattice,  $m(T)$  is the corresponding symmetry-induced multiplicity,  $A_n$  contains the structure factor of the structural units and the type of disorder, and  $\Phi_n$  describes the characteristic modulation of the diffuse phenomenon of dimension  $n$  in the powder pattern. These expressions are given below with the assumption of Gaussian line shapes of width  $D$  for the narrow extension(s). The formulae depend on a factor  $M = A_{1/2}(4k_1^2 - H_0^2)/(32 \ln 2)$ , where  $A_{1/2}$  describes the dependence of the Bragg peaks on the instrumental parameters  $U$ ,  $V$  and  $W$  (see Caglioti *et al.*, 1958),

$$A_{1/2}^2 = U \tan^2 \theta + V \tan \theta + W, \quad (4.2.8.13)$$

and  $k_1 = 1/\lambda$ .

(a) Isotropic diffuse peak around  $T$

$$\Phi_0 = [2\pi(M^2 + D^2)]^{-1/2} (1/T^2) \times \exp\{-(H_0 - T)^2/2(M^2 + D^2)\}. \quad (4.2.8.14)$$

The moduli  $|\mathbf{H}_0|$  and  $T$  enter the exponential, *i.e.* the variation of  $d\sigma/d\Omega$  along  $|\mathbf{H}_0|$  is essential. For broad diffuse peaks ( $M \ll D$ ) the angular dependence is due to  $1/T^2$ , *i.e.* proportional to  $1/\sin^2 \theta$ . This result is valid for diffuse peaks of any shape.

(b) Diffuse streak

$$\Phi_1 = [2\pi(M^2 + D^2)]^{-1/2} \int_{-\infty}^{\infty} (T^2 + H^2)^{-1/2} \times \exp\{-H_0 - (T^2 + H^2)^{1/2}/2(M^2 + D^2)\} dH. \quad (4.2.8.15)$$

The integral has to be evaluated numerically. If  $(M^2 + D^2)$  is not too large, the term  $1/(T^2 + H^2)$  varies only slowly compared to the exponential term and may be kept outside the integral, setting it approximately to  $1/H_0^2$ .

(c) Diffuse plane (with  $R^2 = H_x^2 + H_y^2$ )

$$\Phi_2 = (M^2 + D^2)^{-1/2} \int R^2/(T^2 + R^2) \times \exp\{-H_0 - (T^2 + R^2)^{1/2}/2(M^2 + D^2)\} dR. \quad (4.2.8.16)$$

With the same approximation as in (b) the expression may be simplified to

$$\Phi_2 = \pi/H_0 [1 - \text{erf}\{(T - H_0)/[2(M^2 + D^2)]^{1/2}\} + 1/H_0^2 [2\pi(M^2 + D^2)]^{1/2} \times \exp\{-(H_0 - T)^2/2(M^2 + D^2)\}]. \quad (4.2.8.17)$$

(d) Slowly varying diffuse scattering in three dimensions

$\Phi_3 = \text{constant}$ . Consequently, the intensity is directly proportional to the cross section. The characteristic functions  $\Phi_0$ ,  $\Phi_1$  and  $\Phi_2$  are shown in Fig. 4.2.8.2 for equal values of  $T$  and  $D$ . Note the relative peak shifts and the high-angle tail.

4.2.8.3. Total diffraction pattern

As mentioned in Section 4.2.7.3.2, the atomic pair-distribution function (PDF), which is classically used for the analysis of the atomic distributions in liquids, melts or amorphous samples, can also be used to gain an understanding of disorder in crystals. The PDF is the Fourier transform of the total scattering. The measurement of total scattering is basically similar to recording X-ray or neutron powder patterns. The success of the method depends, however, decisively on various factors: (i) The availability of a large data set, *i.e.* reliable intensities up to high  $H$  values, in order to get rid of truncation ripples, which heavily influence the interpretation. Currently, values of  $H_{\max}$  of more than  $7 \text{ \AA}^{-1}$  can be achieved either with synchrotron X-rays [at the European Synchrotron Radiation Facility (ESRF) or Cornell High Energy Synchrotron Source (CHESS)] or with neutrons from reactors (*e.g.* instrument D4 at the ILL) and spallation sources [at ISIS or at LANSCE (instrument NPDF)]. (ii) High  $H$  resolution. (iii) High intensities, in particular at high  $H$  values. (iv) Low background of any kind which does not originate from the sample. High-quality intensities are therefore to be extracted from the raw data by taking care of an adequate absorption correction, correction of multiple-scattering effects, separation of inelastically scattered radiation (*e.g.* Compton scattering) and careful subtraction of ‘diffuse’ background which is not the ‘true’ diffuse scattering from the sample. These conditions are in practice rather demanding. A further detailed discussion is beyond the scope of this chapter, but a more thorough discussion is given, *e.g.*, by Egami (2004), and some examples are given by Egami & Billinge (2003).

## References

- Adlhart, W. (1981). *Diffraction by crystals with planar domains*. Acta Cryst. **A37**, 794–801.
- Amorós, J. L. & Amorós, M. (1968). *Molecular Crystals: Their Transforms and Diffuse Scattering*. New York: John Wiley.
- Arndt, U. W. (1986a). X-ray position sensitive detectors. J. Appl. Cryst. **19**, 145–163.
- Arndt, U. W. (1986b). The collection of single crystal diffraction data with area detectors. J. Phys. (Paris) Colloq. **47**(C5), 1–6.
- Aroyo, M. I., Boysen, H. & Perez-Mato, J. M. (2002). Inelastic neutron scattering selection rules for phonons: application to leucite phase transitions. Appl. Phys. A, **74**, S1043–S1048.
- Axe, J. D. (1980). Debye-Waller factors for incommensurate structures. Phys. Rev. B, **21**, 4181–4190.
- Bardhan, P. & Cohen, J. B. (1976). X-ray diffraction study of short-range-order structure in a disordered Au<sub>3</sub>Cu alloy. Acta Cryst. **A32**, 597–614.
- Bauer, G., Seitz, E. & Just, W. (1975). Elastic diffuse scattering of neutrons as a tool for investigation of non-magnetic point defects. J. Appl. Cryst. **8**, 162–175.
- Bauer, G. S. (1979). Diffuse elastic neutron scattering from nonmagnetic materials. In *Treatise on Materials Science and Technology*, Vol. 15, edited by G. Kostorz, pp. 291–336. New York: Academic Press.
- Berthold, T. & Jagodzinski, H. (1990). Analysis of the distribution of impurities in crystals by anomalous X-ray scattering. Z. Kristallogr. **193**, 85–100.
- Bessière, M., Lefebvre, S. & Calvayrac, Y. (1983). X-ray diffraction study of short-range order in a disordered Au<sub>3</sub>Cu alloy. Acta Cryst. **B39**, 145–153.
- Beyeler, H. U., Pietronero, L. & Strässler, S. (1980). Configurational model for a one-dimensional ionic conductor. Phys. Rev. B, **22**, 2988–3000.

#### 4. DIFFUSE SCATTERING AND RELATED TOPICS

- Billinge, S. J. L. & Egami, T. (1993). *Short-range atomic structure of  $Nd_{2-x}Ce_xCuO_{4-y}$  determined by real-space refinement of neutron-powder-diffraction data*. *Phys. Rev. B*, **47**, 14386–14406.
- Billinge, S. J. L. & Thorpe, M. F. (1998). *Local Structure from Diffraction*. New York: Plenum Press.
- Boissieu, M. de, Boudard, M., Hennion, M., Bellissent, R., Kycia, S., Goldman, A., Janot, C. & Audier, M. (1995). *Diffuse scattering and phason elasticity in the AlPdMn icosahedral phase*. *Phys. Rev. Lett.* **75**, 89–92.
- Borie, B. & Sparks, C. J. (1971). *The interpretation of intensity distributions from disordered binary alloys*. *Acta Cryst. A* **27**, 198–201.
- Boysen, H. (1985). *Analysis of diffuse scattering in neutron powder diagrams. Applications to glassy carbon*. *J. Appl. Cryst.* **18**, 320–325.
- Boysen, H. (1995). *Diffuse scattering by domains and domain walls*. *Phase Transit.* **55**, 1–16.
- Boysen, H. (1997). *Suppression of subsidiary maxima in computer simulations of diffraction intensities*. *Z. Kristallogr.* **212**, 634–636.
- Boysen, H. (2007). *Coherence effects in the scattering from domain structures*. *J. Phys. Condens. Matter*, **19**, 270526–270537.
- Boysen, H. & Adlhart, W. (1987). *Resolution corrections in diffuse scattering experiments*. *J. Appl. Cryst.* **20**, 200–209.
- Boysen, H. & Frey, F. (1998). *Diffuse scattering: X-rays vs. neutrons*. *Phase Transit.* **67**, 197–217.
- Boysen, H., Frey, F., Schrader, H. & Eckold, G. (1991). *On the proto-to-clino-/orthoenstatite phase transformation: single-crystal X-ray and inelastic neutron investigation*. *Phys. Chem. Mineral.* **17**, 629–635.
- Bradley, C. J. & Cracknell, A. P. (1972). *The Mathematical Theory of Symmetry in Solids*, pp. 51–76. Oxford: Clarendon Press.
- Brämer, R. (1975). *Statistische Probleme der Theorie des Parakristalls*. *Acta Cryst. A* **31**, 551–560.
- Brämer, R. & Ruland, W. (1976). *The limitations of the paracrystalline model of disorder*. *Macromol. Chem.* **177**, 3601–3617.
- Bubeck, E. & Gerold, V. (1984). *An X-ray investigation in the small and wide angle range from G.P.I. zones in Al–Cu*. In *Microstructural Characterization of Materials by Non-Microscopical Techniques*, edited by N. H. Andersen, M. Eldrup, N. Hansen, R. J. Jensen, T. Leffers, H. Lilholt, O. B. Pedersen & B. N. Singh. Roskilde: Risø National Laboratory.
- Burandt, B., Komorek, M., Schnabel, W., Press, W. & Boysen, H. (1992). *High resolution X-ray investigations on the supersatellite reflections of labradorite*. *Z. Kristallogr.* **200**, 141–156.
- Butler, B. D., Haeffner, D. R., Lee, P. L. & Welberry, T. R. (2000). *High-energy X-ray diffuse scattering using Weissenberg flat-cone geometry*. *J. Appl. Cryst.* **33**, 1046–1050.
- Butler, B. D. & Welberry, T. R. (1992). *Calculation of diffuse scattering from simulated disordered crystals: a comparison with optical transforms*. *J. Appl. Cryst.* **25**, 391–399.
- Caglioti, G., Paoletti, A. & Ricci, R. (1958). *Choice of collimators for a crystal spectrometer for neutron diffraction*. *Nucl. Instrum. Methods*, **3**, 223–226.
- Campbell, B. J., Welberry, T. R., Broach, R. W., Hong, H. & Cheetham, A. K. (2004). *Elucidation of zeolite microstructure by synchrotron X-ray diffuse scattering*. *J. Appl. Cryst.* **37**, 187–192.
- Cenedese, P., Bley, F. & Lefebvre, S. (1984). *Diffuse scattering in disordered ternary alloys: neutron measurements of local order in a stainless steel  $Fe_{0.56}Cr_{0.21}Ni_{0.23}$* . *Acta Cryst. A* **40**, 228–240.
- Collongues, R., Fayard, M. & Gautier, F. (1977). *Ordre et désordre dans les solides*. *J. Phys. (Paris) Colloq.* **38**(C7), Suppl.
- Comes, R. & Shirane, G. (1979). *X-ray and neutron scattering from one-dimensional conductors*. In *Highly Conducting One Dimensional Solids*, edited by J. T. Devreese, R. P. Evrard & V. E. Van Doren, ch. 2. New York: Plenum.
- Conradi, E. & Müller, U. (1986). *Fehlordnung bei Verbindungen mit Schichtstrukturen. II. Analyse der Fehlordnung in Wismutriiodid*. *Z. Kristallogr.* **176**, 263–269.
- Convert, P. & Forsyth, J. B. (1983). *Position-Sensitive Detectors of Thermal Neutrons*. London: Academic Press.
- Cooper, M. J. & Nathans, R. (1968a). *The resolution function in neutron diffractometry. II. The resolution function of a conventional two-crystal neutron diffractometer for elastic scattering*. *Acta Cryst. A* **24**, 481–484.
- Cooper, M. J. & Nathans, R. (1968b). *The resolution function in neutron diffractometry. III. Experimental determination and properties of the elastic two-crystal resolution function*. *Acta Cryst. A* **24**, 619–624.
- Courville-Brenasin, J. de, Joyez, G. & Tchoubar, D. (1981). *Méthode d'ajustement automatique entre courbes expérimentale et calculée dans les diagrammes de diffraction de poudre. Cas des solides à structure lamellaire. I. Développement de la méthode*. *J. Appl. Cryst.* **14**, 17–23.
- Cowley, J. M. (1950a). *X-ray measurement of order in single crystals of  $Cu_3Au$* . *J. Appl. Phys.* **21**, 24–36.
- Cowley, J. M. (1950b). *An approximate theory of order in alloys*. *Phys. Rev.* **77**, 664–675.
- Cowley, J. M. (1976a). *Diffraction by crystals with planar faults. I. General theory*. *Acta Cryst. A* **32**, 83–87.
- Cowley, J. M. (1976b). *Diffraction by crystals with planar faults. II. Magnesium fluorogermanate*. *Acta Cryst. A* **32**, 88–91.
- Cowley, J. M. (1981). *Diffraction Physics*, 2nd ed. Amsterdam: North-Holland.
- Cowley, J. M. & Au, A. Y. (1978). *Diffraction by crystals with planar faults. III. Structure analysis using microtwins*. *Acta Cryst. A* **34**, 738–743.
- Cowley, J. M., Cohen, J. B., Salomon, M. B. & Wuensch, B. J. (1979). *Modulated Structures*. AIP Conference Proceedings, No. 53. New York: AIP.
- Dederichs, P. H. (1973). *The theory of diffuse X-ray scattering and its application to the study of point defects and their clusters*. *J. Phys. F*, **3**, 471–496.
- Dolling, G., Powell, B. M. & Sears, V. F. (1979). *Neutron diffraction study of the plastic phases of polycrystalline  $SF_6$  and  $CBr_4$* . *Mol. Phys.* **37**, 1859–1883.
- Dorner, B. & Comes, R. (1977). *Phonons and structural phase transformation*. In *Dynamics of Solids and Liquids by Neutron Scattering*, edited by S. Lovesey & T. Springer, ch. 3. *Topics in Current Physics*, Vol. 3. Berlin: Springer.
- Dorner, C. & Jagodzinski, H. (1972). *Entmischung im System  $SnO_2-TiO_2$* . *Krist. Tech.* **7**, 427–444.
- Dubernat, J. & Pezerat, H. (1974). *Fautes d'empilement dans les oxalates dihydratés des métaux divalents de la série magnésienne (Mg, Fe, Co, Ni, Zn, Mn)*. *J. Appl. Cryst.* **7**, 387–393.
- Edwards, O. S. & Lipson, H. (1942). *Imperfections in the structure of cobalt. I. Experimental work and proposed structure*. *Proc. R. Soc. London Ser. A*, **180**, 268–277.
- Egami, T. (1990). *Atomic correlations in non-periodic matter*. *Mater. Trans. JIM*, **31**, 163–176.
- Egami, T. (2004). *Local crystallography of crystals with disorder*. *Z. Kristallogr.* **219**, 122–129.
- Egami, T. & Billinge, S. J. L. (2003). *Underneath the Bragg Peaks: Structural Analysis of Complex Materials*. Oxford: Pergamon Press.
- Emery, V. J. & Axe, J. D. (1978). *One-dimensional fluctuations and the chain-ordering transformation in  $Hg_{3-\delta}AsF_6$* . *Phys. Rev. Lett.* **40**, 1507–1511.
- Endres, H., Pouget, J. P. & Comes, R. (1982). *Diffuse X-ray scattering and order-disorder effects in the iodine chain compounds  $N,N'$ -diethyl- $N,N'$ -dihydrophenazinium iodide,  $E_2PI_{1.6}$  and  $N,N'$ -dibenzyl- $N,N'$ -dihydrophenazinium iodide,  $B_2PI_{1.6}$* . *J. Phys. Chem. Solids*, **43**, 739–748.
- Epstein, J., Welberry, T. R. & Jones, R. (1982). *Analysis of the diffuse X-ray scattering from substitutionally disordered molecular crystals of monoclinic 9-bromo-10-methylanthracene*. *Acta Cryst. A* **38**, 611–618.
- Estermann, M. & Steurer, W. (1998). *Diffuse scattering data acquisition techniques*. *Phase Transit.* **67**, 165–195.
- Fender, B. E. F. (1973). *Diffuse scattering and the study of defect solids*. In *Chemical Applications of Thermal Neutron Scattering*, edited by B. T. M. Willis, ch. 11. Oxford University Press.
- Flack, H. D. (1970). *Short-range order in crystals of anthrone and in mixed crystals of anthrone-anthraquinone*. *Philos. Trans. R. Soc. London Ser. A*, **266**, 583–591.
- Fontaine, D. de (1972). *An analysis of clustering and ordering in multicomponent solid solutions. I. Stability criteria*. *J. Phys. Chem. Solids*, **33**, 297–310.
- Fontaine, D. de (1973). *An analysis of clustering and ordering in multicomponent solid solutions. II. Fluctuations and kinetics*. *J. Phys. Chem. Solids*, **34**, 1285–1304.
- Forst, R., Jagodzinski, H., Boysen, H. & Frey, F. (1987). *Diffuse scattering and disorder in urea inclusion compounds  $OC(NH_2)_2 + C_nH_{2n+2}$* . *Acta Cryst. B* **43**, 187–197.
- Fouret, P. (1979). *Diffuse X-ray scattering by orientationally disordered solids*. In *The Plastically Crystalline State*, edited by J. N. Sherwood, ch. 3. New York: John Wiley.

## 4.2. DISORDER DIFFUSE SCATTERING OF X-RAYS AND NEUTRONS

- Frey, F. (1997). *Diffuse scattering by domain structures*. In *Local Structure from Diffraction*, edited by S. J. L. Billinge & M. F. Thorpe. New York: Plenum Press.
- Frey, F. (2003). *Disorder diffuse scattering of crystals and quasicrystals*. In *Particle Scattering, X-ray Diffraction, and Microstructure of Solids and Liquids*, edited by M. Ristig & K. Gernoth. Heidelberg: Springer.
- Frey, F. & Boysen, H. (1981). *Disorder in cobalt single crystals*. *Acta Cryst. A* **37**, 819–826.
- Frey, F., Jagodzinski, H. & Steger, W. (1986). *On the phase transformation zinc blende to wurtzite*. *Bull. Minéral. Crystallogr.* **109**, 117–129.
- Frey, F. & Weidner, E. (2002). *Diffraction by domains in decagonal Al-Co-Ni quasicrystals*. *J. Alloys Compd.* **342**, 105–109.
- Frey, F. & Weidner, E. (2003). *Disorder in decagonal quasicrystals*. *Z. Kristallogr.* **218**, 160–169.
- Fultz, B. & Howe, J. M. (2002). *Transmission Electron Microscopy and Diffractometry of Materials*, ch. 9. Heidelberg: Springer.
- Gehlen, P. & Cohen, J. B. (1965). *Computer simulation of the structure associated with local order in alloys*. *Phys. Rev. A*, **139**, 844–855.
- Georgopoulos, P. & Cohen, J. B. (1977). *The determination of short range order and local atomic displacements in disordered binary solid solutions*. *J. Phys. (Paris) Colloq.* **38**(C7), 191–196.
- Gerlach, P., Schärf, O., Prandl, W. & Dorner, B. (1982). *Separation of the coherent and incoherent scattering of  $C_2Cl_6$  by polarization analysis*. *J. Phys. (Paris) Colloq.* **43**(C7), 151–157.
- Gerold, V. (1954). *Röntgenographische Untersuchungen über die Aushärtung einer Aluminium-Kupfer-Legierung mit Kleinwinkel-Schwenkaufnahmen*. *Z. Metallkd.* **45**, 593–607.
- Gibbons, P. C. & Kelton, K. F. (1993). *Arcs of diffuse scattering in icosahedral glass models*. *J. Non-Cryst. Solids*, **153&154**, 165–171.
- Goff, J. P., Hayes, W., Hull, S., Hutching, M. T. & Clausen, K. N. (1999). *Defect structure of yttria-stabilized zirconia and its influence on the ionic conductivity at elevated temperatures*. *Phys. Rev. B*, **59**, 14202–14219.
- Goldman, A. I., Guryan, C. A., Stephens, P. W., Parsey, J. M. Jr, Aepli, G., Chen, H. S. & Gayle, F. W. (1988). *Diffuse scattering from the icosahedral phase alloys*. *Phys. Rev. Lett.* **61**, 1962–1965.
- Gragg, J. E., Hayakawa, M. & Cohen, J. B. (1973). *Errors in qualitative analysis of diffuse scattering from alloys*. *J. Appl. Cryst.* **6**, 59–66.
- Guinier, A. (1942). *Le mécanisme de la précipitation dans un cristal de solution solide métallique. Cas des systèmes aluminium–cuivre et aluminium–argent*. *J. Phys. Radium*, **8**, 124–136.
- Guinier, A. (1963). *X-ray Diffraction in Crystals, Imperfect Solids and Amorphous Bodies*. San Francisco: Freeman.
- Halla, F., Jagodzinski, H. & Ruston, W. R. (1953). *One-dimensional disorder in dodecahydrotriphenylene,  $C_{18}H_{24}$* . *Acta Cryst.* **6**, 478–488.
- Harada, J., Iwata, H. & Ohshima, K. (1984). *A new method for the measurement of X-ray diffuse scattering with a combination of an energy dispersive detector and a source of white radiation*. *J. Appl. Cryst.* **17**, 1–6.
- Harburn, G., Miller, J. S. & Welberry, T. R. (1974). *Optical-diffraction screens containing large numbers of apertures*. *J. Appl. Cryst.* **7**, 36–38.
- Harburn, G., Taylor, C. A. & Welberry, T. R. (1975). *An Atlas of Optical Transforms*. London: Bell.
- Hashimoto, S. (1974). *Correlative microdomain model for short range ordered alloy structures. I. Diffraction theory*. *Acta Cryst. A* **30**, 792–798.
- Hashimoto, S. (1981). *Correlative microdomain model for short range ordered alloy structures. II. Application to special cases*. *Acta Cryst. A* **37**, 511–516.
- Hashimoto, S. (1983). *Correlative microdomain model for short range ordered alloy structures. III. Analysis for diffuse scattering from quenched CuAu alloy*. *Acta Cryst. A* **39**, 524–530.
- Hashimoto, S. (1987). *Intensity expression for short-range order diffuse scattering with ordering energies in a ternary alloy system*. *J. Appl. Cryst.* **20**, 182–186.
- Haubold, H. G. (1975). *Measurement of diffuse X-ray scattering between reciprocal lattice points as a new experimental method in determining interstitial structures*. *J. Appl. Cryst.* **8**, 175–183.
- Hayakawa, M. & Cohen, J. B. (1975). *Experimental considerations in measurements of diffuse scattering*. *Acta Cryst. A* **31**, 635–645.
- Hendricks, S. B. & Teller, E. (1942). *X-ray interference in partially ordered layer lattices*. *J. Chem. Phys.* **10**, 147–167.
- Hohlwein, D., Hoser, A. & Prandl, W. (1986). *Orientational disorder in cubic  $CsNO_2$  by neutron powder diffraction*. *Z. Kristallogr.* **177**, 93–102.
- Hosemann, R. (1975). *Micro paracrystallites and paracrystalline superstructures*. *Macromol. Chem. Suppl.* **1**, pp. 559–577.
- Hosemann, R. & Bagchi, S. N. (1962). *Direct Analysis of Diffraction by Matter*. Amsterdam: North-Holland.
- Iizumi, M. (1973). *Lorentz factor in single crystal neutron diffraction*. *Jpn. J. Appl. Phys.* **12**, 167–172.
- Ishii, T. (1983). *Static structure factor of Frenkel–Kontorova-systems at high temperatures. Application to K-hollandite*. *J. Phys. Soc. Jpn.* **52**, 4066–4073.
- Jagodzinski, H. (1949a). *Eindimensionale Fehlordnung und ihr Einfluss auf die Röntgeninterferenzen. I. Berechnung des Fehlordnungsgrades aus den Röntgeninterferenzen*. *Acta Cryst.* **2**, 201–208.
- Jagodzinski, H. (1949b). *Eindimensionale Fehlordnung und ihr Einfluss auf die Röntgeninterferenzen. II. Berechnung der fehlgeordneten dichtesten Kugelpackungen mit Wechselwirkungen der Reichweite 3*. *Acta Cryst.* **2**, 208–214.
- Jagodzinski, H. (1949c). *Eindimensionale Fehlordnung und ihr Einfluss auf die Röntgeninterferenzen. III. Vergleich der Berechnungen mit experimentellen Ergebnissen*. *Acta Cryst.* **2**, 298–304.
- Jagodzinski, H. (1954). *Der Symmetrieeinfluss auf den allgemeinen Lösungsansatz eindimensionaler Fehlordnungsprobleme*. *Acta Cryst.* **7**, 17–25.
- Jagodzinski, H. (1963). *On disorder phenomena in crystals*. In *Crystallography and Crystal Perfection*, edited by G. N. Ramachandran, pp. 177–188. London: Academic Press.
- Jagodzinski, H. (1964a). *Allgemeine Gesichtspunkte für die Deutung diffuser Interferenzen von fehlgeordneten Kristallen*. In *Advances in Structure Research by Diffraction Methods*, Vol. 1, edited by R. Brill & R. Mason, pp. 167–198. Braunschweig: Vieweg.
- Jagodzinski, H. (1964b). *Diffuse disorder scattering by crystals*. In *Advanced Methods of Crystallography*, edited by G. N. Ramachandran, pp. 181–219. London: Academic Press.
- Jagodzinski, H. (1968). *Fokussierende Monochromatoren für Einkristallverfahren?* *Acta Cryst.* **B24**, 19–23.
- Jagodzinski, H. (1972). *Transformation from cubic to hexagonal silicon carbide as a solid state reaction*. *Kristallografiya*, **16**, 1235–1246.
- Jagodzinski, H. (1987). *Diffuse X-ray scattering from crystals*. In *Progress in Crystal Growth and Characterization*, edited by P. Krishna, pp. 47–102. Oxford: Pergamon Press.
- Jagodzinski, H. & Haefner, K. (1967). *On order-disorder in ionic non-stoichiometric crystals*. *Z. Kristallogr.* **125**, 188–200.
- Jagodzinski, H. & Hellner, E. (1956). *Die eindimensionale Phasenumwandlung des  $RhSn_2$* . *Z. Kristallogr.* **107**, 124–149.
- Jagodzinski, H. & Korekawa, M. (1965). *Supersatelliten im Beugungsbild des Labradorits ( $Ca_2Na(Si_2Al)_2O_8$ )*. *Naturwissenschaften*, **52**, 640–641.
- Jagodzinski, H. & Korekawa, M. (1973). *Diffuse X-ray scattering by lunar minerals*. *Geochim. Cosmochim. Acta Suppl.* **4**, 1, 933–951.
- Jagodzinski, H. & Laves, R. (1947). *Über die Deutung der Entmischungsvorgänge in Mischkristallen unter besonderer Berücksichtigung der Systeme Aluminium–Kupfer und Aluminium–Silber*. *Z. Metallkd.* **40**, 296–305.
- Jagodzinski, H. & Penzkofer, B. (1981). *A new type of satellite in plagioclases*. *Acta Cryst. A* **37**, 754–762.
- James, R. W. (1954). *The Optical Principles of Diffraction of X-rays*, ch. X. London: Bell.
- Janner, A. & Janssen, T. (1980a). *Symmetry of incommensurate crystal phases. I. Commensurate basic structures*. *Acta Cryst. A* **36**, 399–408.
- Janner, A. & Janssen, T. (1980b). *Symmetry of incommensurate crystal phases. II. Incommensurate basic structures*. *Acta Cryst. A* **36**, 408–415.
- Janssen, T. & Janner, A. (1987). *Incommensurability in crystals*. *Adv. Phys.* **36**, 519–624.
- Jaric, M. V. & Nelson, D. R. (1988). *Diffuse scattering from quasicrystals*. *Phys. Rev. B*, **37**, 4458–4472.
- Jefferey, J. W. (1953). *Unusual X-ray diffraction effects from a crystal of wollastonite*. *Acta Cryst.* **6**, 821–826.
- Jones, R. C. (1949). *X-ray diffraction by randomly oriented line gratings*. *Acta Cryst.* **2**, 252–257.
- Kaiser-Bischoff, I., Boysen, H., Frey, F., Hoffmann, J.-U., Hohlwein, D. & Lerch, M. (2005). *The defect structure of Y- and N-doped zirconia*. *J. Appl. Cryst.* **38**, 139–146.
- Kakinoki, J. & Komura, Y. (1954). *Intensity of X-ray diffraction by a one-dimensionally disordered crystal. I. General derivation in the cases of ‘Reichweite’ s = 0 and s = 1*. *J. Phys. Soc. Jpn.* **9**, 169–183.
- Kakinoki, J. & Komura, Y. (1965). *Diffraction by a one-dimensionally disordered crystal. I. The intensity equation*. *Acta Cryst.* **19**, 137–147.

#### 4. DIFFUSE SCATTERING AND RELATED TOPICS

- Kalning, M., Dorna, V., Press, W., Kek, S. & Boysen, H. (1997). *Profile analysis of the supersatellite reflections in labradorite – A synchrotron X-ray diffraction study*. *Z. Kristallogr.* **212**, 545–549.
- Keen, D. A. & Nield, V. M. (2004). *Diffuse Neutron Scattering from Crystalline Materials*. Oxford University Press.
- Kitaigorodsky, A. I. (1984). *Mixed Crystals. Springer Series in Solid State Science*, Vol. 33, chs. 6.4, 6.5, 8.4. Berlin: Springer.
- Klug, H. P. & Alexander, L. E. (1954). *X-ray Diffraction Procedures*. New York: John Wiley.
- Korekawa, M. (1967). *Theorie der Satellitenreflexe*. Habilitationsschrift der Naturwissenschaftlichen Fakultät der Universität München, Germany.
- Korekawa, M. & Jagodzinski, H. (1967). *Die Satellitenreflexe des Labradorits*. *Schweiz. Mineral. Petrogr. Mitt.* **47**, 269–278.
- Krivoglaz, M. A. (1969). *Theory of X-ray and Thermal Neutron Scattering by Real Crystals*. Part I. New York: Plenum.
- Krivoglaz, M. A. (1996a). *Diffuse Scattering of X-rays and Neutrons by Fluctuations*. Berlin: Springer.
- Krivoglaz, M. A. (1996b). *X-ray and Neutron Diffraction in Nonideal Crystals*. Berlin: Springer.
- Lechner, R. E. & Riekel, C. (1983). Application of neutron scattering in chemistry. In *Neutron Scattering and Muon Spin Rotation. Springer Tracts in Modern Physics*, Vol. 101, edited by G. Höhler, pp. 1–84. Berlin: Springer.
- Lefebvre, J., Fouret, R. & Zeyen, C. (1984). Structure determination of sodium nitrate near the order-disorder phase transition. *J. Phys. (Paris)*, **45**, 1317–1327.
- Lei, J., Wang, R., Hu, Ch. & Ding, D. (1999). Diffuse scattering from decagonal quasicrystals. *Phys. Rev. B*, **59**, 822–828.
- McGreevy, R. L. (2001). Reverse Monte Carlo modelling. *J. Phys. Condens. Matter*, **13**, R877–R913.
- McGreevy, R. L. & Pusztai, L. (1988). Reverse Monte Carlo simulation: a new technique for the determination of disordered structures. *Mol. Simul.* **1**, 359–367.
- Mardix, S. & Steinberger, I. T. (1970). Tilt and structure transformation in ZnS. *J. Appl. Phys.* **41**, 5339–5341.
- Martorana, A., Marigo, A., Toniolo, L. & Zenetti, R. (1986). Stacking faults in the  $\beta$ -form of magnesium dichloride. *Z. Kristallogr.* **176**, 1–12.
- Matsubara, E. & Georgopoulos, P. (1985). Diffuse scattering measurements with synchrotron radiation: instrumentation and techniques. *J. Appl. Cryst.* **18**, 377–383.
- Metropolis, N., Rosenbluth, A. W., Rosenbluth, M. N., Teller, A. H. & Teller, E. (1953). Equation of state calculations by fast computing machines. *J. Chem. Phys.* **21**, 1087–1092.
- Micu, A. M. & Smith, J. C. (1995). SERENA: a program for calculating X-ray diffuse scattering intensities from molecular dynamics trajectories. *Comput. Phys. Commun.* **91**, 331–338.
- More, M., Lefebvre, J. & Hennion, B. (1984). Quasi-elastic coherent neutron scattering in the disordered phase of  $CBr_4$ . Experimental evidence of local order and rotational dynamics of molecules. *J. Phys. (Paris)*, **45**, 303–307.
- More, M., Lefebvre, J., Hennion, B., Powell, B. M. & Zeyen, C. (1980). Neutron diffuse scattering in the disordered phase of  $CBr_4$ . I. Experimental. Elastic and quasi-elastic coherent scattering in single crystals. *J. Phys. C*, **13**, 2833–2846.
- Moss, D. S., Harris, G. W., Wostrack, A. & Sansom, C. (2003). Diffuse X-ray scattering from molecular crystals. *Crystallogr. Rev.* **9**, 229–277.
- Moss, S. C. (1966). Local order in solid alloys. In *Local Atomic Arrangements Studied by X-ray Diffraction*, edited by J. B. Cohen & J. E. Hilliard, ch. 3, pp. 95–122. New York: Gordon and Breach.
- Müller, H. (1952). Die eindimensionale Umwandlung Zinkblendewurtzit und die dabei auftretenden Anomalien. *Neues Jahrb. Mineral. Abh.* **84**, 43–76.
- Neder, R. B., Frey, F. & Schulz, H. (1990). Diffraction theory for diffuse scattering by correlated microdomains in materials with several atoms per unit cell. *Acta Cryst.* **A46**, 792–798.
- Nield, V. M. & Keen, D. A. (2001). *Diffuse Neutron Scattering from Crystalline Materials*. Oxford Science Publications.
- Nield, V. M., Keen, D. A. & McGreevy, R. L. (1995). The interpretation of single-crystal diffuse scattering using reverse Monte Carlo modelling. *Acta Cryst.* **A51**, 763–771.
- Niimura, N. (1986). Evaluation of data from 1-d PSD used in TOF method. *J. Phys. (Paris) Colloq.* **47**(C5), Suppl., 129–136.
- Niimura, N., Chataka, T., Ostermann, A., Kurihara, K. & Tanaka, I. (2003). High resolution neutron protein crystallography. Hydrogen and hydration in proteins. *Z. Kristallogr.* **218**, 96–107.
- Niimura, N., Ishikawa, Y., Arai, M. & Furusaka, M. (1982). Applications of position sensitive detectors to structural analysis using pulsed neutron sources. *AIP Conference Proceedings*, Vol. 89, *Neutron Scattering*, edited by J. Faber, pp. 11–22. New York: AIP.
- Ohshima, K. & Harada, J. (1986). X-ray diffraction study of short-range ordered structure in a disordered Ag–15 at.% Mg alloy. *Acta Cryst.* **B42**, 436–442.
- Ohshima, K., Harada, J., Morinaga, M., Georgopoulos, P. & Cohen, J. B. (1986). Report on a round-robin study of diffuse X-ray scattering. *J. Appl. Cryst.* **19**, 188–194.
- Ohshima, K. & Moss, S. C. (1983). X-ray diffraction study of basal-(ab)-plane structure and diffuse scattering from silver atoms in disordered stage-2  $Ag_{0.18}TiS_2$ . *Acta Cryst.* **A39**, 298–305.
- Ohshima, K., Watanabe, D. & Harada, J. (1976). X-ray diffraction study of short-range order diffuse scattering from disordered Cu–29.8% Pd alloy. *Acta Cryst.* **A32**, 883–892.
- Overhauser, A. W. (1971). Observability of charge-density waves by neutron diffraction. *Phys. Rev. B*, **3**, 3173–3182.
- Pandey, D., Lele, S. & Krishna, P. (1980a). X-ray diffraction from one dimensionally disordered 2H-crystals undergoing solid state transformation to the 6H structure. I. The layer displacement mechanism. *Proc. R. Soc. London Ser. A*, **369**, 435–439.
- Pandey, D., Lele, S. & Krishna, P. (1980b). X-ray diffraction from one dimensionally disordered 2H-crystals undergoing solid state transformation to the 6H structure. II. The deformation mechanism. *Proc. R. Soc. London Ser. A*, **369**, 451–461.
- Pandey, D., Lele, S. & Krishna, P. (1980c). X-ray diffraction from one dimensionally disordered 2H-crystals undergoing solid state transformation to the 6H structure. III. Comparison with experimental observations on SiC. *Proc. R. Soc. London Ser. A*, **369**, 463–477.
- Patterson, A. L. (1959). Fourier theory. In *International Tables for X-ray Crystallography*, Vol. II, ch. 2.5. Birmingham: Kynoch Press.
- Peisl, J. (1975). Diffuse X-ray scattering from the displacement field of point defects and defect clusters. *J. Appl. Cryst.* **8**, 143–149.
- Perez-Mato, J. M., Aroyo, M., Hlinka, J., Quilichini, M. & Currat, R. (1998). Phonon symmetry selection rules for inelastic neutron scattering. *Phys. Rev. Lett.* **81**, 2462–2465.
- Petricek, V., Maly, K., Coppens, P., Bu, X., Cisarova, I. & Frost-Jensen, A. (1991). The description and analysis of composite crystals. *Acta Cryst.* **A47**, 210–216.
- Pflanz, S. & Moritz, W. (1992). The domain matrix method: a new calculation scheme for diffraction profiles. *Acta Cryst.* **A48**, 716–727.
- Pouget, J.-P. (2004). X-ray diffuse scattering as precursor of incommensurate Peierls transitions in one-dimensional organic transfer conductors. *Z. Kristallogr.* **219**, 711–718.
- Prandl, W. (1981). The structure factor of orientational disordered crystals: the case of arbitrary space, site, and molecular point-group. *Acta Cryst.* **A37**, 811–818.
- Press, W. (1973). Analysis of orientational disordered structures. I. Method. *Acta Cryst.* **A29**, 252–256.
- Press, W., Grimm, H. & Hüller, A. (1979). Analysis of orientational disordered structures. IV. Correlations between orientation and position of a molecule. *Acta Cryst.* **A35**, 881–885.
- Press, W. & Hüller, A. (1973). Analysis of orientational disordered structures. II. Examples: Solid  $CD_4$ ,  $p$ - $D_2$  and  $NDBr_4$ . *Acta Cryst.* **A29**, 257–263.
- Proffen, Th. & Neder, R. B. (1999). DISCUS, a program for diffuse scattering and defect-structure simulations – update. *J. Appl. Cryst.* **32**, 838–839.
- Proffen, Th. & Welberry, T. R. (1997). Analysis of diffuse scattering via reverse Monte Carlo technique: a systematic investigation. *Acta Cryst.* **A53**, 202–216.
- Radons, W., Keller, J. & Geisel, T. (1983). Dynamical structure factor of a 1-d harmonic liquid: comparison of different approximation methods. *Z. Phys. B*, **50**, 289–296.
- Rahman, S. H. (1993). The local domain configuration in partially ordered  $AuCu_3$ . *Acta Cryst.* **A49**, 68–79.
- Rietveld, H. M. (1969). A profile refinement method for nuclear and magnetic structures. *J. Appl. Cryst.* **2**, 65–71.
- Rosshirt, E., Frey, F. & Boysen, H. (1991). Disorder diffuse scattering in K-hollandite. *Neues Jahrb. Mineral. Abh.* **1**, 101–115.

## 4.2. DISORDER DIFFUSE SCATTERING OF X-RAYS AND NEUTRONS

- Rosshirt, E., Frey, F., Boysen, H. & Jagodzinski, H. (1985). *Chain ordering in  $E_2PI_{1.6}$  (5,10-diethylphenazinium iodide)*. *Acta Cryst.* **B41**, 66–76.
- Sabine, T. M. & Clarke, P. J. (1977). *Powder neutron diffraction – refinement of the total pattern*. *J. Appl. Cryst.* **10**, 277–280.
- Scaringe, P. R. & Ibers, J. A. (1979). *Application of the matrix method to the calculation of diffuse scattering in linearly disordered crystals*. *Acta Cryst. A***35**, 803–810.
- Schmatz, W. (1973). *X-ray and neutron scattering on disordered crystals*. In *Treatise on Materials Science and Technology*, Vol. 2, edited by H. Hermans, ch. 3.1. New York: Academic Press.
- Schmatz, W. (1983). *Neutron scattering studies of lattice defects: static properties of defects*. In *Methods of Experimental Physics, Solid State: Nuclear Physics*, Vol. 21, edited by J. N. Mundy, S. J. Rothman, M. J. Fluss & L. C. Smetskajew, ch. 3.1. New York: Academic Press.
- Schulz, H. (1982). *Diffuse X-ray diffraction and its application to materials research*. In *Current Topics in Materials Science*, edited by E. Kaldis, ch. 4. Amsterdam: North-Holland.
- Schwartz, L. H. & Cohen, J. B. (1977). *Diffraction from Materials*. New York: Academic Press.
- Schweika, W. (1998). *Diffuse scattering and Monte Carlo simulations*. Springer Tracts in Modern Physics, Volume 141, edited by G. Höhler. Heidelberg: Springer.
- Schweika, W. (2003). *Time-of-flight and vector polarization analysis for diffuse scattering*. *Physica B*, **335**, 157–163.
- Schweika, W. & Böni, P. (2001). *The instrument DNS: Polarization analysis for diffuse neutron scattering*. *Physica B*, **297**, 155–159.
- Sherwood, J. N. (1979). *The Plastically Crystalline State*. New York: John Wiley.
- Smaalen, S. van (2004). *An elementary introduction to superspace crystallography*. *Z. Kristallogr.* **219**, 681–691.
- Smaalen, S. van, Lamfers, H.-J. & de Boer, J. L. (1998). *Diffuse scattering and order in quasi-one-dimensional molecular crystals*. *Phase Transit.* **67**, 277–294.
- Sparks, C. J. & Borie, B. (1966). *Methods of analysis for diffuse X-ray scattering modulated by local order and atomic displacements*. In *Atomic Arrangements Studied by X-ray Diffraction*, edited by J. B. Cohen & J. E. Hilliard, ch. 1, pp. 5–50. New York: Gordon and Breach.
- Springer, T. (1972). *Quasielastic Neutron Scattering for the Investigation of Diffuse Motions in Solid and Liquids*. Springer Tracts in Modern Physics, Vol. 64. Berlin: Springer.
- Steurer, W. & Frey, F. (1998). *Disorder diffuse scattering from quasicrystals*. *Phase Transit.* **67**, 319–361.
- Takaki, Y. & Sakurai, K. (1976). *Intensity of X-ray scattering from one-dimensionally disordered crystal having the multilayer average structure*. *Acta Cryst. A***32**, 657–663.
- Tibbals, J. E. (1975). *The separation of displacement and substitutional disorder scattering: a correction for structure factor ratio variation*. *J. Appl. Cryst.* **8**, 111–114.
- Turberfield, K. C. (1970). *Time-of-flight diffractometry*. In *Thermal Neutron Diffraction*, edited by B. T. M. Willis. Oxford University Press.
- Vainshtein, B. K. (1966). *Diffraction of X-rays by Chain Molecules*. Amsterdam: Elsevier.
- Varn, D. P., Canright, G. S. & Crutchfield, J. P. (2002). *Discovering planar disorder in closed-packed structures from X-ray diffraction: Beyond the fault model*. *Phys. Rev. B*, **66**, 174110–174113.
- Warren, B. E. (1941). *X-ray diffraction in random layer lattices*. *Phys. Rev.* **59**, 693–699.
- Warren, B. E. (1969). *X-ray Diffraction*. Reading: Addison-Wesley.
- Weber, T. & Bürgi, H.-B. (2002). *Determination and refinement of disordered crystal structures using evolutionary algorithms in combination with Monte Carlo methods*. *Acta Cryst. A***58**, 526–540.
- Weber, Th. (2005). *Cooperative evolution – a new algorithm for the investigation of disordered structures via Mont Carlo modelling*. *Z. Kristallogr.* **220**, 1099–1107.
- Weber, Th., Boysen, H. & Frey, F. (2000). *Longitudinal positional ordering of n-alkane molecules in urea inclusion compounds*. *Acta Cryst. B***56**, 132–141.
- Weidner, E., Frey, F. & Hradil, K. (2001). *Transient ordering states in decagonal Al-Co-Ni and Al-Cu-Co-Si phases*. *Philos. Mag.* **201**, 2375–2389.
- Weidner, E., Frey, F., Lei, J.-L., Pedersen, B., Paulmann, C. & Morgenroth, W. (2004). *Disordered quasicrystals: diffuse scattering in decagonal Al-Ni-Fe*. *J. Appl. Cryst.* **37**, 802–807.
- Welberry, T. R. (1983). *Routine recording of diffuse scattering from disordered molecular crystals*. *J. Appl. Phys.* **59**, 192–197.
- Welberry, T. R. (1985). *Diffuse X-ray scattering and models of disorder*. *Rep. Prog. Phys.* **48**, 1543–1593.
- Welberry, T. R. (2004). *Diffuse X-ray Scattering and Models of Disorder*. Oxford University Press.
- Welberry, T. R. & Butler, B. D. (1994). *Interpretation of diffuse X-ray scattering via models of disorder*. *J. Appl. Cryst.* **27**, 205–231.
- Welberry, T. R. & Glazer, A. M. (1985). *A comparison of Weissenberg and diffractometer methods for the measurement of diffuse scattering from disordered molecular crystals*. *Acta Cryst. A***41**, 394–399.
- Welberry, T. R., Goossens, D. J., Haeffner, D. R., Lee, P. L. & Almer, J. (2003). *High-energy diffuse scattering on the 1-ID beamline at the Advanced Photon Source*. *J. Synchrotron Rad.* **10**, 284–286.
- Welberry, T. R. & Proffen, Th. (1998). *Analysis of diffuse scattering from single crystals via the reverse Monte Carlo technique. I. Comparison with direct Monte Carlo*. *J. Appl. Cryst.* **31**, 309–317.
- Welberry, T. R., Proffen, Th. & Bown, M. (1998). *Analysis of single-crystal diffuse X-ray scattering via automatic refinement of a Monte Carlo model*. *Acta Cryst. A***54**, 661–674.
- Welberry, T. R. & Siripitayananon, J. (1986). *Analysis of the diffuse scattering from disordered molecular crystals: application to 1,4-dibromo-2,5-diethyl-3,6-dimethylbenzene at 295 K*. *Acta Cryst. B***42**, 262–272.
- Welberry, T. R. & Siripitayananon, J. (1987). *Analysis of the diffuse scattering from disordered molecular crystals: application to 1,3-dibromo-2,5-diethyl-4,6-dimethylbenzene at 295 K*. *Acta Cryst. B***43**, 97–106.
- Welberry, T. R. & Withers, R. L. (1987). *Optical transforms of disordered systems displaying diffuse intensity loci*. *J. Appl. Cryst.* **20**, 280–288.
- Welberry, T. R. & Withers, R. L. (1990). *Optical transforms of disordered systems containing symmetry-related scattering sites*. *J. Appl. Cryst.* **23**, 303–314.
- Wilke, W. (1983). *General lattice factor of the ideal paracrystal*. *Acta Cryst. A***39**, 864–867.
- Wilson, A. J. C. (1942). *Imperfections in the structure of cobalt. II. Mathematical treatment of proposed structure*. *Proc. R. Soc. London Ser. A*, **180**, 277–285.
- Wilson, A. J. C. (1949). *X-ray diffraction by random layers: ideal line profiles and determination of structure amplitudes from observed line profiles*. *Acta Cryst. 2*, 245–251.
- Wilson, A. J. C. (1962). *X-ray Optics*, 2nd ed., chs. V, VI, VIII. London: Methuen.
- Windsor, C. G. (1982). *Neutron diffraction performance in pulsed and steady sources*. In *Neutron Scattering*. AIP Conference Proceedings, Vol. 89, edited by J. Faber, pp. 1–10. New York: AIP.
- Wolff, P. M. de (1974). *The pseudo-symmetry of modulated crystal structures*. *Acta Cryst. A***30**, 777–785.
- Wolff, P. M. de, Janssen, T. & Janner, A. (1981). *The superspace groups for incommensurate crystal structures with a one-dimensional modulation*. *Acta Cryst. A***37**, 625–636.
- Wong, S. F., Gillan, B. E. & Lucas, B. W. (1984). *Single crystal disorder diffuse X-ray scattering from phase II ammonium nitrate,  $NH_4NO_3$* . *Acta Cryst. B***40**, 342–346.
- Wooster, W. A. (1962). *Diffuse X-ray Reflections from Crystals*, chs. IV, V. Oxford: Clarendon Press.
- Wu, T. B., Matsubara, E. & Cohen, J. B. (1983). *New procedures for qualitative studies of diffuse X-ray scattering*. *J. Appl. Cryst.* **16**, 407–414.
- Yessik, M., Werner, S. A. & Sato, H. (1973). *The dependence of the intensities of diffuse peaks on scattering angle in neutron diffraction*. *Acta Cryst. A***29**, 372–382.
- Young, R. A. (1975). Editor. *International discussion meeting on studies of lattice distortions and local atomic arrangements by X-ray, neutron and electron diffraction*. *J. Appl. Cryst.* **8**, 79–191.
- Zernike, F. & Prins, J. A. (1927). *Die Beugung von Röntgenstrahlen in Flüssigkeiten als Effekt der Molekülordnung*. *Z. Phys.* **41**, 184–194.