

1.3. ELASTIC PROPERTIES

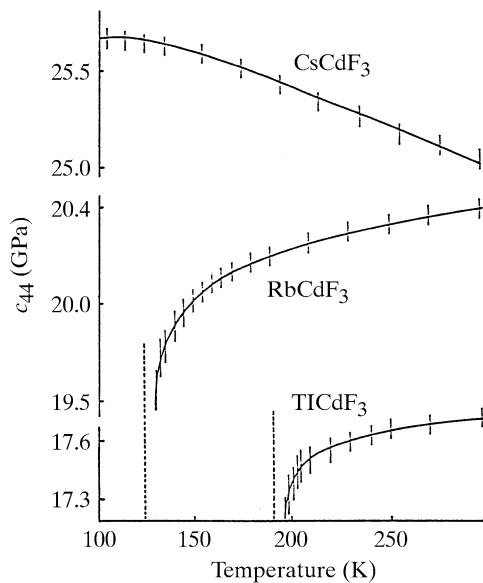


Fig. 1.3.5.3. Temperature dependence of the elastic constant c_{44} in RbCdF_3 , CsCdF_3 and TiCdF_3 crystals; the crystals of RbCdF_3 and TiCdF_3 undergo structural phase transitions (after Rousseau *et al.*, 1975).

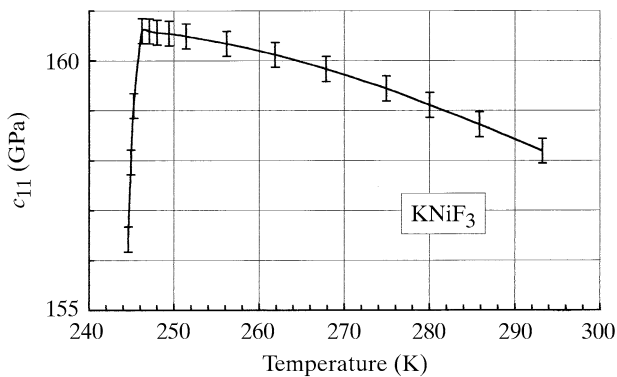


Fig. 1.3.5.4. Temperature dependence of the elastic constant c_{11} in KNiF_3 , which undergoes a para-antiferromagnetic phase transition. Reprinted with permission from *Appl. Phys. Lett.* (Nouet *et al.*, 1972). Copyright (1972) American Institute of Physics.

temperature when this constant is the order parameter or is strongly coupled to the order parameter of the transformation; for instance, in the cooperative Jahn–Teller phase transition in DyVO_4 , $(c_{11} - c_{12})/2$ is the soft acoustic phonon mode leading to the phase transition and this parameter anticipates the phase transition 300 K before it occurs (Fig. 1.3.5.5).

1.3.5.3. Pressure dependence of the elastic constants

As mentioned above, anharmonic potentials are needed to explain the stress dependence of the elastic constants of a crystal. Thus, if the strain-energy density is developed in a polynomial in terms of the strain, only the first and the second elastic constants are used in linear elasticity (harmonic potentials), whereas higher-order elastic constants are also needed for nonlinear elasticity (anharmonic potentials).

Concerning the pressure dependence of the elastic constants (nonlinear elastic effect), considerable attention has been paid to

Table 1.3.5.2. Order of magnitude of the temperature dependence of the elastic stiffnesses for different types of crystals

Type of crystal	$(\partial \ln c_{11} / \partial \Theta)_p$ (K^{-1})	$(\partial \ln c_{44} / \partial \Theta)_p$ (K^{-1})
Ionic	-10^{-3}	-3×10^{-4}
Covalent	-10^{-4}	-8×10^{-5}
Metallic	-2×10^{-4}	-3×10^{-4}

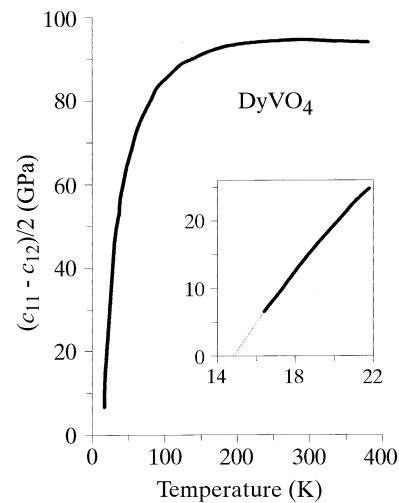


Fig. 1.3.5.5. Temperature dependence of $(c_{11} - c_{12})/2$ in DyVO_4 , which undergoes a cooperative Jahn–Teller phase transition (after Melcher & Scott, 1972).

their experimental determination since they are a unique source of significant information in many fields:

(i) In *geophysics*, a large part of the knowledge we have on the interior of the earth comes from the measurement of the transit time of elastic bursts propagating in the mantle and in the core (in the upper mantle, the average pressure is estimated to be about a few hundred GPa, a value which is comparable to that of the elastic stiffnesses of many materials).

(ii) In *solid-state physics*, the pressure dependence of the elastic constants gives significant indications concerning the stability of crystals. For example, Fig. 1.3.5.2 shows the pressure dependence of the elastic constants of KZnF_3 , a cubic crystal belonging to the perovskite family. As mentioned previously, this crystal is known to be stable over a wide range of temperature and the elastic stiffnesses c_{ij} depend linearly on pressure. It may be noted that, consequently, the third-order elastic constants (TOECs) are constant. On the contrary, we observe in Fig. 1.3.5.6 that the pressure dependence of the elastic constants of TiCdF_3 , a cubic crystal belonging to the same family but which is known to become unstable when the temperature is decreased to 191 K (Fischer, 1982), is nonlinear even at low pressures. In this case, the development of the strain-energy density in terms of strains elastic constant; the contributions of the fourth- and fifth-order elastic constants are not negligible.

(iii) For practical use in the case of technical materials such as concrete or worked metals, the pressure dependence of the elastic moduli is also required for examining the effect of applied stresses or of an applied hydrostatic pressure, and for studying residual stresses resulting from loading (heating) and unloading (cooling) the materials.

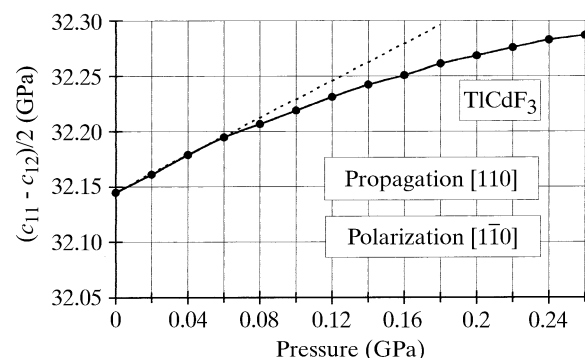


Fig. 1.3.5.6. Pressure dependence of the elastic constants $(c_{11} - c_{12})/2$ in TiCdF_3 . Reproduced with permission from *Ultrasonics Symposium Proc. IEEE* (Fischer *et al.*, 1980). Copyright (1980) IEEE.