

1.1. OVERVIEW AND PRINCIPLES

$$\mathbf{a} = \frac{1}{V^*}(\mathbf{b}^* \times \mathbf{c}^*), \quad \mathbf{b} = \frac{1}{V^*}(\mathbf{c}^* \times \mathbf{a}^*), \quad \mathbf{c} = \frac{1}{V^*}(\mathbf{a}^* \times \mathbf{b}^*). \quad (1.1.15)$$

The relationship between the reciprocal and the real lattice parameters expressed geometrically rather than in the vector formalism used above is

$$\begin{aligned} a^* &= \frac{bc \sin \alpha}{V}, \\ b^* &= \frac{ac \sin \beta}{V}, \\ c^* &= \frac{ab \sin \gamma}{V}, \\ \cos \alpha^* &= \frac{\cos \beta \cos \gamma - \cos \alpha}{\sin \beta \sin \gamma}, \\ \cos \beta^* &= \frac{\cos \alpha \cos \gamma - \cos \beta}{\sin \alpha \sin \gamma}, \\ \cos \gamma^* &= \frac{\cos \alpha \cos \beta - \cos \gamma}{\sin \alpha \sin \beta}, \\ V &= abc \sqrt{1 + 2 \cos \alpha \cos \beta \cos \gamma - \cos^2 \alpha - \cos^2 \beta - \cos^2 \gamma}. \end{aligned} \quad (1.1.16)$$

Equation (1.1.16) is the most general expression for non-orthogonal lattices. The expressions simplify considerably for higher-symmetry crystal systems.

We now re-derive Bragg's law using the vector notation introduced above (Fig. 1.1.6). The wave vectors of the incoming and outgoing beams are given by \mathbf{s}_0 and \mathbf{s} , respectively. They point in the direction of propagation of the wave and their length depends on λ . For elastic scattering (for which there is no change in wavelength on scattering), \mathbf{s}_0 and \mathbf{s} have the same length.

We define the scattering vector as

$$\mathbf{h} = (\mathbf{s} - \mathbf{s}_0), \quad (1.1.17)$$

which for a specular reflection is always perpendicular to the scattering plane. The length of \mathbf{h} is given by

$$\frac{h}{s} = 2 \sin \theta. \quad (1.1.18)$$

Comparison with the formula for the Bragg equation (1.1.3),

$$\frac{n\lambda}{d} = 2 \sin \theta, \quad (1.1.19)$$

gives

$$\frac{n\lambda}{d} = \frac{h}{s}. \quad (1.1.20)$$

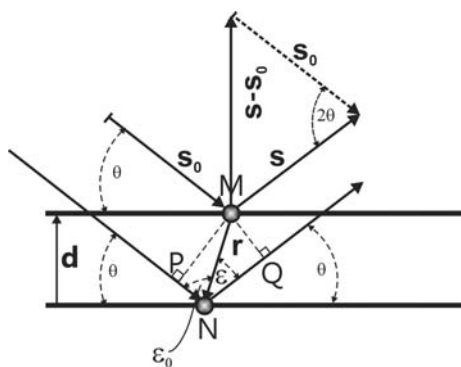


Figure 1.1.6 Illustration of the important wave and scattering vectors in the case of elastic Bragg scattering. [Reproduced from Dinnebier & Billinge (2008) with permission from the Royal Society of Chemistry.]

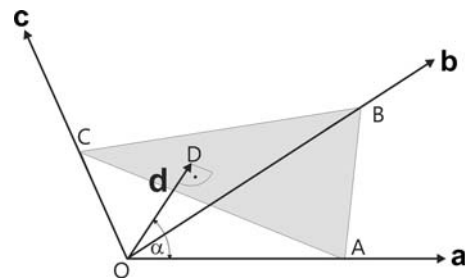


Figure 1.1.7 Geometrical description of a lattice plane in terms of real-space basis vectors. The arc and dot below the letter D indicate a right angle. [Reproduced from Dinnebier & Billinge (2008) with permission from the Royal Society of Chemistry.]

Setting the magnitude of \mathbf{s} to $1/\lambda$, we get the Bragg equation in terms of the magnitude h of the scattering vector,

$$h = \frac{n}{d}. \quad (1.1.21)$$

This shows that diffraction occurs when the magnitude of the scattering vector is an integral number of reciprocal-lattice spacings $1/d$. We define a vector \mathbf{d}^* perpendicular to the lattice planes with length $1/d$. Since \mathbf{h} is perpendicular to the scattering plane, this leads to

$$\mathbf{h} = n\mathbf{d}^*. \quad (1.1.22)$$

Diffraction can occur at different scattering angles 2θ for the same crystallographic plane, giving the different orders n of diffraction. For simplicity, the number n will be incorporated in the indexing of the lattice planes, where

$$d_{nh,nk,nl}^* = nd_{hkl}^*, \quad (1.1.23)$$

e.g., $d_{222}^* = 2d_{111}^*$, and we get an alternative expression for Bragg's equation:

$$\mathbf{h} = \mathbf{d}_{hkl}^*. \quad (1.1.24)$$

The vector \mathbf{d}_{hkl}^* points in a direction perpendicular to a real-space lattice plane. We would like to express this vector in terms of the reciprocal-space basis vectors \mathbf{a}^* , \mathbf{b}^* , \mathbf{c}^* .

First we define \mathbf{d}_{hkl} in terms of the real-space basis vectors \mathbf{a} , \mathbf{b} , \mathbf{c} . Referring to Fig. 1.1.7, we can define

$$\mathbf{OA} = \frac{1}{h}\mathbf{a}, \quad \mathbf{OB} = \frac{1}{k}\mathbf{b}, \quad \mathbf{OC} = \frac{1}{l}\mathbf{c} \quad (1.1.25)$$

with h , k and l being integers, as required by the periodicity of the lattice.

The plane-normal vector \mathbf{d}_{hkl} originates on one plane and terminates on the next parallel plane. Therefore, $\mathbf{OA} \cdot \mathbf{d} = (\mathbf{OA})d \cos \alpha$. From Fig. 1.1.7 we see that, geometrically, $(\mathbf{OA}) \cos \alpha = d$. Substituting, we get $\mathbf{OA} \cdot \mathbf{d} = d^2$. Combining this with equation (1.1.25) leads to

$$\frac{1}{h}\mathbf{a} \cdot \mathbf{d} = d^2 \quad (1.1.26)$$

and consequently

$$h = \mathbf{a} \cdot \frac{\mathbf{d}}{d^2}, \quad k = \mathbf{b} \cdot \frac{\mathbf{d}}{d^2}, \quad l = \mathbf{c} \cdot \frac{\mathbf{d}}{d^2}. \quad (1.1.27)$$

By definition, h , k and l are divided by their largest common integer to be Miller indices. The vector \mathbf{d}_{hkl}^* , from Bragg's equation (1.1.24), points in the plane-normal direction parallel to \mathbf{d} but with length $1/d$. We can now write \mathbf{d}_{hkl}^* in terms of the