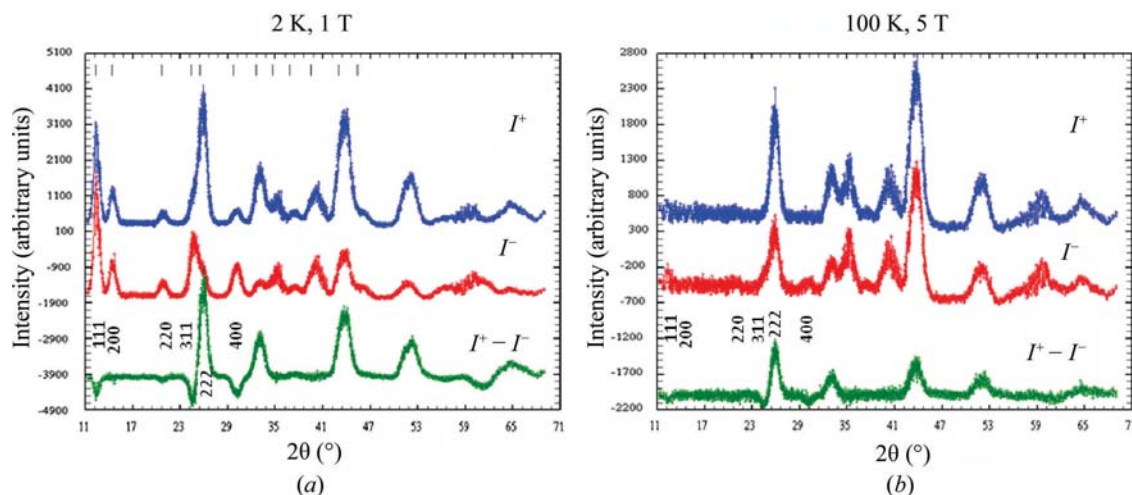


2. INSTRUMENTATION AND SAMPLE PREPARATION

**Figure 2.8.17**

Polarized neutron diffraction patterns for $\text{Tb}_2\text{Sn}_2\text{O}_7$ at 2 K and 1 T (a) and 100 K and 5 T (b). I^+ and I^- are the intensities for spin-up and spin-down neutrons, respectively. Taken from Gukasov & Brown (2010). Copyright IOP Publishing. Reproduced with permission. All rights reserved.

& Brown, 2010). No magnetic contribution to the diffracted intensities was observed at 2 K in the absence of an external field. However, applying a field led to considerable changes in the diffraction pattern (Fig. 2.8.17). At 100 K and 5 T, the intensities of the reflections that are allowed for the cubic space group $Fd\bar{3}m$ increase considerably. Furthermore, they were found to depend strongly on the polarization of the incoming neutrons, as shown by the difference pattern in Fig. 2.8.17. At a field of 1 T, new reflections appear (Fig. 2.8.17a) that are forbidden for the occupied sites in $Fd\bar{3}m$ symmetry, such as 200, 222 and 240. The intensities of these new reflections do not change with the polarization of the neutrons, as demonstrated in the difference plot, hence they are purely magnetic. In conclusion, information on local anisotropic magnetic susceptibility at different sites can be obtained by using a combination of unpolarized and polarized neutron powder patterns. This demonstrates the usefulness of polarized neutron scattering, even for polycrystalline samples.

We now return to X-ray investigations of magnetic materials. A laboratory device for fields up to 5 T and temperatures above room temperature was mentioned in Section 2.8.3.3.1. The corresponding low-temperature apparatus (Koyama *et al.*, 2013) has produced results on magneto-caloric compounds of $\text{MnFeP}_{1-x}\text{Z}_x$ with $Z = \text{As}$ or Ge produces materials that exhibit a large magneto-caloric effect and thus allows control of the Curie temperature by chemical composition. Studies under magnetic fields are mandatory, as the refrigerants are working under a field. For two different compositions of the As compound the lattice parameters change drastically and the cell volume decreases with increasing magnetic field strength. In $\text{MnFeP}_{0.78}\text{Ge}_{0.22}$ a field-induced ferromagnetic phase was observed near the Curie temperature at 280 K. This phase is, however, not identical to the low-temperature ferromagnetic one (Koyama *et al.*, 2013).

2.8.3.3.4. Concluding remarks

Despite some shortcomings, powder diffraction studies as a function of magnetic fields are valuable for the qualitative and sometimes even quantitative interpretation of magnetic materials. Unpolarized neutrons are used in most experiments, but the additional information from polarized neutrons has also been exploited. X-rays do not interact directly with the magnetic moments, but structural changes as a consequence of magnetic phase transitions have been observed in several cases. *In situ* powder diffraction under magnetic fields reaching 4 T on an

X-ray diffractometer with a rotating anode revealed details of lattice parameters and atomic positions in rare-earth alloys with a higher precision than that accessible by neutron diffraction (Pecharsky *et al.*, 2007). Furthermore, the two test-case compounds studied, Gd_5Ge_4 and DyCo_2 , contain the rare-earth elements Gd and Dy with the highest absorption cross sections for neutrons in their natural isotope abundance. The data were used to refine the underlying structure models by Rietveld analysis. Advances in X-ray and neutron sources and optics delivered higher resolution and flux to the samples, which in combination with rapid computing made real-time experiments feasible.

2.8.4. Summary

We have shown here that *in situ* studies under electric and magnetic fields are in a well advanced state. Laboratory equipment can be used for diverse experiments where changes occur on a timescale that can be followed with an exposure time of minutes. Real progress is, however, achieved by using high-energy synchrotron radiation and by using neutrons, which can penetrate larger volumes. Thus *in operando* studies of real devices are feasible. In addition to such diffraction experiments, which provide average information on a macroscopic length scale, complementary experiments like electron microscopy are vital for revealing local structural information. Only the combination of several methods can give sufficient insight into structure–property relationships and the functionality of materials.

References

- Adam, R., Wadewitz, D., Gruner, W., Klemm, V., Ehrenberg, H. & Rafaja, D. (2013). *Phase and microstructure development in the conversion type electrodes for Li-ion batteries based on the Cu-Fe-O system*. *J. Electrochem. Soc.* **160**, A1594–A1603.
- Anastasopoulos, M., Bebb, R., Berry, K., Birch, J., Bryś, T., Buffet, J.-C., Clergeau, J.-F., Deen, P. P., Ehlers, G., van Esch, P., Everett, S. M., Guerard, B., Hall-Wilton, R., Herwig, K., Hultman, L., Höglund, C., Iruretagoiena, I., Issa, F., Jensen, J., Khaplanov, A., Kirstein, O., Higuera, I. L., Piscitelli, F., Robinson, L., Schmidt, S. & Stefanescu, I. (2017). *Multi-grid detector for neutron spectroscopy: results obtained on time-of-flight spectrometer CNCS*. *J. Instrum.* **12**, P04030.
- Anton, E.-M., Schmitt, L. A., Hinterstein, M., Trodahl, J., Kowalski, B., Jo, W., Kleebe, H.-J., Rödel, J. & Jones, J. L. (2012). *Structure and temperature-dependent phase transitions of lead-free $\text{Bi}_{1/2}\text{Na}_{1/2}\text{TiO}_3$ – $\text{Bi}_{1/2}\text{K}_{1/2}\text{TiO}_3$ – $\text{K}_{0.5}\text{Na}_{0.5}\text{NbO}_3$ piezoceramics*. *J. Mater. Res.* **27**, 2466–2478.

2.8. POWDER DIFFRACTION IN ELECTRIC AND MAGNETIC FIELDS

- Ballabriga, R., Campbell, M., Heijne, E. H. M., Llopart, X. & Tlustos, L. (2007). *The Medipix3 prototype, a pixel readout chip working in single photon counting mode with improved spectrometric performance*. *IEEE Trans. Nucl. Sci.* **54**, 1824–1829.
- Bergamaschi, A., Cervellino, A., Dinapoli, R., Gozzo, F., Henrich, B., Johnson, I., Kraft, P., Mozzanica, A., Schmitt, B. & Shi, X. (2009). *Photon counting microstrip detector for time resolved powder diffraction experiments*. *Nucl. Instrum. Methods Phys. Res. A*, **604**, 136–139.
- Bergstöm, Ö., Andersson, A. M., Edström, K. & Gustafsson, T. (1998). *A neutron diffraction cell for studying lithium-insertion processes in electrode materials*. *J. Appl. Cryst.* **31**, 823–825.
- Bergström, O., Gustafsson, T. & Thomas, J. O. (1998). *An X-ray powder diffraction attachment for in situ studies of ion insertion processes in electrode materials*. *J. Appl. Cryst.* **31**, 103–105.
- Bird, M. D., Hongyu Bai, Bole, S., Jingping Chen, Dixon, I. R., Ehmler, H., Gavrilin, A. V., Painter, T. A., Smeibidl, P., Toth, J., Weijers, H., Ting Xu & Zhai, Y. (2009). *The NHMFL hybrid magnet projects*. *IEEE Trans. Appl. Supercond.* **19**, 1612–1616.
- Brown, F. J. (2010). *Aspects of superconducting magnet design for neutron scattering sample environments*. *J. Phys. Conf. Ser.* **251**, 012093.
- Cabana, J., Monconduit, L., Larcher, D. & Palacín, M. (2010). *Beyond intercalation-based Li-ion batteries: the state of the art and challenges of electrode materials reacting through conversion reactions*. *Adv. Mater.* **22**, E170–E192.
- Cartier, S., Bergamaschi, A., Dinapoli, R., Greiffenberg, D., Johnson, I., Jungmann, J. H., Mezza, D., Mozzanica, A., Schmitt, B., Shi, X., Stapanoni, M., Sun, J. & Tinti, G. (2014). *Micron resolution of MÖNCH and GOTTHARD, small pitch charge integrating detectors with single photon sensitivity*. *J. Instrum.* **9**, C05027.
- Choe, H., Gorfman, S., Hinterstein, M., Ziolkowski, M., Knapp, M., Heidbrink, S., Vogt, M., Bednarcik, J., Berghäuser, A., Ehrenberg, H. & Pietsch, U. (2015). *Combining high time and angular resolutions: time-resolved X-ray powder diffraction using a multi-channel analyser detector*. *J. Appl. Cryst.* **48**, 970–974.
- Daniels, J. E. & Drakopoulos, M. (2009). *High-energy X-ray diffraction using the Pixium 4700 flat-panel detector*. *J. Synchrotron Rad.* **16**, 463–468.
- Daniels, J. E., Finlayson, T. R., Studer, A. J., Hoffman, M. & Jones, J. L. (2007). *Time-resolved diffraction measurements of electric-field-induced strain in tetragonal lead zirconate titanate*. *J. Appl. Phys.* **101**, 094104.
- Daniels, J. E., Jo, W., Rödel, J., Honkimäki, V. & Jones, J. L. (2010). *Electric-field-induced phase-change behavior in $(\text{Bi}_{0.5}\text{Na}_{0.5})\text{TiO}_3\text{-BaTiO}_3\text{-(K}_{0.5}\text{Na}_{0.5})\text{NbO}_3$: a combinatorial investigation*. *Acta Mater.* **58**, 2103–2111.
- Eckold, G., Schober, H. & Nagler, S. E. (2010). Editors. *Studying Kinetics with Neutrons*. Springer Series in Solid State Sciences. Berlin, Heidelberg: Springer.
- Eriksson, T., Andersson, A. M., Bergström, Ö., Edström, K., Gustafsson, T. & Thomas, J. O. (2001). *A furnace for in situ X-ray diffraction studies of insertion processes in electrode materials at elevated temperatures*. *J. Appl. Cryst.* **34**, 654–657.
- Fuess, H., Bertaut, E. F., Pauthenet, R. & Durif, A. (1970). *Structure aux rayons X, neutrons et propriétés magnétiques des orthovanadates de nickel et de cobalt*. *Acta Cryst.* **B26**, 2036–2046.
- Gukasov, A. & Brown, P. J. (2010). *Determination of atomic site susceptibility tensors from neutron diffraction data on polycrystalline samples*. *J. Phys. Condens. Matter.* **22**, 502201.
- Hansen, T. C., Henry, P. F., Fischer, H. E., Torregrossa, J. & Convert, P. (2008). *The D20 instrument at the ILL: a versatile high-intensity two-axis neutron diffractometer*. *Meas. Sci. Technol.* **19**, 034001.
- Herklotz, M., Scheiba, F., Hinterstein, M., Nikolowski, K., Knapp, M., Dippel, A.-C., Giebeler, L., Eckert, J. & Ehrenberg, H. (2013). *Advances in in situ powder diffraction of battery materials: a case study of the new beamline P02.1 at DESY, Hamburg*. *J. Appl. Cryst.* **46**, 1117–1127.
- Hinterstein, M. (2011). *Mikrostrukturanalyse von Piezokeramiken mit Hilfe von Synchrotron- und Neutronenstrahlung*. Goettingen: Sierke Verlag.
- Hinterstein, M., Hoelzel, M., Rouquette, J., Haines, J., Glaum, J., Kungl, H. & Hoffman, M. (2015). *Interplay of strain mechanisms in morphotropic piezoceramics*. *Acta Mater.* **94**, 319–327.
- Hinterstein, M., Knapp, M., Hölzel, M., Jo, W., Cervellino, A., Ehrenberg, H. & Fuess, H. (2010). *Field-induced phase transition in $\text{Bi}_{1/2}\text{Na}_{1/2}\text{TiO}_3$ -based lead-free piezoelectric ceramics*. *J. Appl. Cryst.* **43**, 1314–1321.
- Hinterstein, M., Rouquette, J., Haines, J., Papet, P., Glaum, J., Knapp, M., Eckert, J. & Hoffman, M. (2014). *Structural contribution to the ferroelectric fatigue in lead zirconate titanate ceramics*. *Phys. Rev. B*, **90**, 094113.
- Hinterstein, M., Rouquette, J., Haines, J., Papet, Ph., Knapp, M., Glaum, J. & Fuess, H. (2011). *Structural description of the macroscopic piezo- and ferroelectric properties of lead zirconate titanate*. *Phys. Rev. Lett.* **107**, 077602.
- Hinterstein, M., Schmitt, L. A., Hoelzel, M., Jo, W., Rödel, J., Kleebe, H.-J. & Hoffman, M. (2015). *Cyclic electric field response of morphotropic $\text{Bi}_{1/2}\text{Na}_{1/2}\text{TiO}_3\text{-BaTiO}_3$ piezoceramics*. *Appl. Phys. Lett.* **106**, 222904.
- Hirota, K., Wakimoto, S. & Cox, D. E. (2006). *Neutron and X-ray scattering studies of relaxors*. *J. Phys. Soc. Jpn.* **75**, 111006.
- Hodeau, J. L., Bordet, P., Anne, M., Prat, A., Fitch, A. N., Dooryheé, E., Vaughan, G. & Freund, A. (1998). *Nine-crystal multianalyzer stage for high-resolution powder diffraction between 6 keV and 40 keV*. *Proc. SPIE*, **3448**, 353–361.
- Hoelzel, M., Senyshyn, A., Gilles, R., Boysen, H. & Fuess, H. (2007). *Scientific review: the structure powder diffractometer SPODI*. *Neutron News*, **18**, 23–26.
- Hoelzel, M., Senyshyn, A., Juenke, N., Boysen, H., Schmahl, W. & Fuess, H. (2012). *High-resolution neutron powder diffractometer SPODI at research reactor FRM II*. *Nucl. Instrum. Methods Phys. Res. A*, **667**, 32–37.
- Hoffmann, M. J., Hammer, M., Endriss, A. & Lupascu, D. C. (2001). *Correlation between microstructure, strain behavior, and acoustic emission of soft PZT ceramics*. *Acta Mater.* **49**, 1301–1310.
- Jin, Y. M., Wang, Y. U., Khachatryan, A. G., Li, J. E. & Viehland, D. (2003). *Conformal miniaturization of domains with low domain-wall energy: monoclinic ferroelectric states near the morphotropic phase boundaries*. *Phys. Rev. Lett.* **91**, 197601.
- Johnsen, R. E. & Norby, P. (2013). *Capillary-based micro-battery cell for in situ X-ray powder diffraction studies of working batteries: a study of the initial intercalation and deintercalation of lithium into graphite*. *J. Appl. Cryst.* **46**, 1537–1543.
- Johnson, I., Bergamaschi, A., Billich, H., Cartier, S., Dinapoli, R., Greiffenberg, D., Guizar-Sicairos, M., Henrich, B., Jungmann, J., Mezza, D., Mozzanica, A., Schmitt, B., Shi, X. & Tinti, G. (2014). *Eiger: a single-photon counting X-ray detector*. *J. Instrum.* **9**, C05032.
- Jones, J. L. (2007). *The use of diffraction in the characterization of piezoelectric materials*. *J. Electroceram.* **19**, 69–81.
- Jones, J., Hoffman, M., Daniels, J. E. & Studer, A. J. (2006). *Direct measurement of the domain switching contribution to the dynamic piezoelectric response in ferroelectric ceramics*. *Appl. Phys. Lett.* **89**, 092901.
- Jones, J. L., Pramanick, A., Nino, J. C., Maziar Motahari, S., Üstündag, E., Daymond, M. R. & Oliver, E. C. (2007). *Time-resolved and orientation-dependent electric-field-induced strains in lead zirconate titanate ceramics*. *Appl. Phys. Lett.* **90**, 172909.
- Kenzelmann, M., Harris, A. B., Aharony, A., Entin-Wohlman, O., Yildirim, T., Huang, Q., Park, S., Lawes, G., Broholm, C., Rogado, N., Cava, R. J., Kim, K. H., Jorge, G. & Ramirez, A. P. (2006). *Field dependence of magnetic ordering in kagomé-staircase compound*. *Phys. Rev. B*, **74**, 014429.
- Kimura, H., Kamada, Y., Noda, Y., Wakimoto, S., Kaneko, K., Metoki, N., Kakurai, K. & Kohn, K. (2007). *Field-induced dielectric and magnetic phase transitions in multiferroic compounds of RMn_2O_5 ($R = \text{Er}, \text{Ho}$)*. *J. Korean Phys. Soc.* **51**, 870–873.
- Kimura, H., Noda, Y. & Kohn, K. (2009). *Spin-driven ferroelectricity in the multiferroic compounds of RMn_2O_5* . *J. Magn. Magn. Mater.* **321**, 854–857.
- Kimura, T., Goto, T., Shintani, H., Ishizaka, K., Arima, T. & Tokura, Y. (2003). *Magnetic control of ferroelectric polarization*. *Nature*, **426**, 55–58.
- Köhli, M., Allmendinger, F., Häußler, W., Schröder, T., Klein, M., Meven, M. & Schmidt, U. (2016). *Efficiency and spatial resolution of the CASCADE thermal neutron detector*. *Nucl. Instrum. Methods Phys. Res. A*, **828**, 242–249.
- Koyama, K., Watanabe, K., Tegus, O., Brück, E., Buschow, K. H. J. & de Boer, F. R. (2013). *X-ray powder diffraction studies on $\text{MnFeP}_{0.78}\text{Ge}_{0.22}$ in high magnetic fields*. *J. Low Temp. Phys.* **170**, 279–284.

2. INSTRUMENTATION AND SAMPLE PREPARATION

- Kraft, P., Bergamaschi, A., Bronnimann, Ch., Dinapoli, R., Eikenberry, E. F., Graafsma, H., Henrich, B., Johnson, I., Kobas, M., Mozzanica, A., Schlepütz, C. M. & Schmitt, B. (2009). *Characterization and calibration of PILATUS detectors*. *IEEE Trans. Nucl. Sci.* **56**, 758–764.
- Lee, P. L., Shu, D., Ramanathan, M., Preissner, C., Wang, J., Beno, M. A., Von Dreele, R. B., Ribaud, L., Kurtz, C., Antao, S. M., Jiao, X. & Toby, B. H. (2008). *A twelve-analyzer detector system for high-resolution powder diffraction*. *J. Synchrotron Rad.* **15**, 427–432.
- Levin, I., Reaney, I. M., Anton, E.-M., Jo, W., Rödel, J., Pokorny, J., Schmitt, L. A., Kleebe, H.-J., Hinterstein, M. & Jones, J. L. (2013). *Local structure, pseudosymmetry, and phase transitions in $\text{Na}_{1/2}\text{Bi}_{1/2}\text{TiO}_3$ - $\text{K}_{1/2}\text{Bi}_{1/2}\text{TiO}_3$ ceramics*. *Phys. Rev. B*, **87**, 024113.
- Liss, K. D., Hunter, B., Hagen, M., Noakes, T. & Kennedy, S. (2006). *Echidna – the new high-resolution powder diffractometer being built at OPAL*. *Physica B*, **385–386**, 1010–1012.
- Liu, L., Knapp, M., Ehrenberg, H., Fang, L., Fan, H., Schmitt, L. A., Fuess, H., Hoelzel, M., Dammak, H., Thi, M. P. & Hinterstein, M. (2017). *Average vs. local structure and composition-property phase diagram of $\text{K}_{0.5}\text{Na}_{0.5}\text{NbO}_3$ - $\text{Bi}_{1/2}\text{Na}_{1/2}\text{TiO}_3$ system*. *J. Eur. Ceram. Soc.* **37**, 1387–1399.
- Mikhailova, D., Schwarz, B., Senyshyn, A., Bell, A. M. T., Skourski, Y., Ehrenberg, H., Tsirlin, A. A., Agrestini, S., Rotter, M., Reichel, P., Chen, J. M., Hu, Z., Li, Z. M., Li, Z. F. & Tjeng, L. H. (2012). *Magnetic properties and crystal structure of SrCoIrO and SrNiIrO* . *Phys. Rev. B*, **86**, 134409.
- Mitsui, Y., Koyama, K. & Watanabe, K. (2009). *X-ray diffraction measurements in high magnetic fields and at high temperatures*. *Sci. Technol. Adv. Mater.* **10**, 014612.
- Mitteemeijer, E. J. & Welzel, U. (2012). Editors. *Modern Diffraction Methods*. Weinheim: Wiley-VCH.
- Morcrette, M., Rozier, P., Dupont, L., Mugnier, E., Sannier, L., Galy, J. & Tarascon, J.-M. (2003). *A reversible copper extrusion–insertion electrode for rechargeable Li batteries*. *Nat. Mater.* **2**, 755–761.
- Mozzanica, A., Bergamaschi, A., Cartier, S., Dinapoli, R., Greiffenberg, D., Johnson, I., Jungmann, J., Maliakal, D., Mezza, D., Ruder, C., Schaedler, L., Schmitt, B., Shi, X. & Tinti, G. (2014). *Prototype characterization of the JUNGFRU pixel detector for SwissFEL*. *J. Instrum.* **9**, C05010.
- Nikolowski, K., Baecht, C., Bramnik, N. N. & Ehrenberg, H. (2005). *A Swagelok-type in situ cell for battery investigations using synchrotron radiation*. *J. Appl. Cryst.* **38**, 851–853.
- Noheda, B., Gonzalo, J. A., Cross, L. E., Guo, R., Park, S. E., Cox, D. E. & Shirane, G. (2000). *Tetragonal-to-monoclinic phase transition in a ferroelectric perovskite: the structure of $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$* . *Phys. Rev. B*, **61**, 8687–8695.
- Ohzuku, T., Ueda, A. & Nagayama, M. (1993). *Electrochemistry and structural chemistry of LiNiO_2 ($R3m$) for 4 volt secondary lithium cells*. *J. Electrochem. Soc.* **140**, 1862–1870.
- Oswald, S., Nikolowski, K. & Ehrenberg, H. (2009). *Quasi in situ XPS investigations on intercalation mechanisms in Li-ion battery materials*. *Anal. Bioanal. Chem.* **393**, 1871–1877.
- Patterson, B. D., Brönnimann, C., Maden, D., Gozzo, F., Groso, A., Schmitt, B., Stampanoni, M. & Willmott, P. R. (2005). *The materials science beamline at the Swiss Light Source*. *Nucl. Instrum. Methods Phys. Res. B*, **238**, 224–228.
- Pecharsky, V. K., Mudryk, Ya. & Gschneidner, K. A. Jr (2007). *In-situ powder diffraction in high magnetic fields*. *Z. Kristallogr. Suppl.* **26**, 139–145.
- Peral, I., McKinlay, J., Knapp, M. & Ferrer, S. (2011). *Design and construction of multicrystal analyser detectors using Rowland circles: application to MAD26 at ALBA*. *J. Synchrotron Rad.* **18**, 842–850.
- Poikela, T., Plosila, J., Westerlund, T., Campbell, M., Gaspari, M. D., Llopart, X., Gromov, V., Kluit, R., van Beuzekom, M., Zappone, F., Zivkovic, V., Brezina, C., Desch, K., Fu, Y. & Kruth, A. (2014). *Timepix3: a 65k channel hybrid pixel readout chip with simultaneous ToA/ToT and sparse readout*. *J. Instrum.* **9**, C05013.
- Poizot, P., Laruelle, S., Grugeon, S., Dupont, L. & Tarascon, J.-M. (2000). *Nano-sized transition-metal oxides as negative-electrode materials for lithium-ion batteries*. *Nature*, **407**, 496–499.
- Pramanick, A., Prewitt, A. D., Cottrell, M. A., Lee, W., Studer, A. J., An, K., Hubbard, C. R. & Jones, J. L. (2010). *In situ neutron diffraction studies of a commercial, soft lead zirconate titanate ceramic: response to electric fields and mechanical stress*. *Appl. Phys. A*, **99**, 557–564.
- Prokhnenko, O., Stein, W.-D., Bleif, H.-J., Fromme, M., Bartkowiak, M. & Wilpert, T. (2015). *Time-of-flight extreme environment diffractometer at the Helmholtz-Zentrum Berlin*. *Rev. Sci. Instrum.* **86**, 033102.
- Radaelli, P. G. & Chapon, L. C. (2008). *A neutron diffraction study of RMn_2O_5 multiferroics*. *J. Phys. Condens. Matter*, **20**, 434213.
- Repper, J., Keller, T., Hofmann, M., Kremaszky, C., Werner, E. & Petry, W. (2009). *Neutron Larmor diffraction for the determination of absolute lattice spacing*. *Adv. X-ray Anal.* **52**, 201–208.
- Schmitt, B., Brönnimann, C., Eikenberry, E. F., Gozzo, F., Hoermann, C., Horisberger, R. & Patterson, B. (2003). *Mythen detector system*. *Nucl. Instrum. Methods Phys. Res. A*, **501**, 267–272.
- Schmitt, L. A., Hinterstein, M., Kleebe, H.-J. & Fuess, H. (2010). *Comparative study of two lead-free piezoceramics using diffraction techniques*. *J. Appl. Cryst.* **43**, 805–810.
- Schmitt, L. A., Schönau, K. A., Theissmann, R., Fuess, H., Kungl, H. & Hoffmann, M. J. (2007). *Composition dependence of the domain configuration and size in $\text{Pb}[\text{Zr}_{1-x}\text{Ti}_x]\text{O}_3$ ceramics*. *J. Appl. Phys.* **101**, 074107.
- Schneider-Muntau, H.-J., Gavrilin, A. V. & Swenson, C. A. (2006). *Magnet technology beyond 50 T*. *IEEE Trans. Appl. Supercond.* **16**, 926–933.
- Schönau, K. A., Knapp, M., Kungl, H., Hoffmann, M. J. & Fuess, H. (2007). *In situ synchrotron diffraction investigation of morphotropic $\text{Pb}[\text{Zr}_{1-x}\text{Ti}_x]\text{O}_3$ under an applied electric field*. *Phys. Rev. B*, **76**, 144112.
- Schönau, K. A., Schmitt, L. A., Knapp, M., Fuess, H., Eichel, R., Kungl, H. & Hoffmann, M. J. (2007). *Nanodomain structure of $\text{Pb}[\text{Zr}_{1-x}\text{Ti}_x]\text{O}_3$ at its morphotropic phase boundary: investigations from local to average structure*. *Phys. Rev. B*, **75**, 184117.
- Sears, V. F. (1992). *Neutron scattering lengths and cross sections*. *Neutron News*, **3**, 26–37.
- Senyshyn, A., Dolotko, O., Mühlbauer, M. J., Nikolowski, K., Fuess, H. & Ehrenberg, H. (2013). *Lithium intercalation into graphitic carbons revisited: experimental evidence for twisted bilayer behavior*. *J. Electrochem. Soc.* **160**, A3198–A3205.
- Senyshyn, A., Mühlbauer, M. J., Dolotko, O., Hofmann, M. & Ehrenberg, H. (2015). *Homogeneity of lithium distribution in cylinder-type Li-ion batteries*. *Sci. Rep.* **5**, 18380.
- Senyshyn, A., Mühlbauer, M. J., Nikolowski, K., Pirling, T. & Ehrenberg, H. (2012). *‘In-operando’ neutron scattering studies on Li-ion batteries*. *J. Power Sources*, **203**, 126–129.
- Shirane, G. (1959). *A note on the magnetic intensities of powder neutron diffraction*. *Acta Cryst.* **12**, 282–285.
- Stefanescu, I., Christensen, M., Fenske, J., Hall-Wilton, R., Henry, P. F., Kirstein, O., Müller, M., Nowak, G., Pooley, D., Raspino, D., Rhodes, N., Šaroun, J., Schefer, J., Schooneveld, E., Sykora, J. & Schweika, W. (2017). *Neutron detectors for the ESS diffractometers*. *J. Instrum.* **12**, P01019.
- Studer, A. J., Hagen, M. E. & Noakes, T. J. (2006). *Wombat: the high-intensity powder diffractometer at the OPAL reactor*. *Physica B*, **385–386**, 1013–1015.
- Suard, E. & Hewat, A. (2001). *The super-D2B project at the ILL*. *Neutron News*, **12**, 30–33.
- Toraya, H., Hibino, H. & Ohsumi, K. (1996). *A new powder diffractometer for synchrotron radiation with a multiple-detector system*. *J. Synchrotron Rad.* **3**, 75–83.
- Weirich, T. E., Lábár, J. L. & Zuo, X. (2006). Editors. *Electron Crystallography. Nato Science Series, Series II: Mathematics, Physics and Chemistry*, Vol. 211. Heidelberg: Springer-Verlag.
- Whittingham, M. S. (1976). *Electrical energy storage and intercalation chemistry*. *Science*, **192**, 1126–1127.
- Wilson, N. R., Petrenko, O. A. & Chapon, L. C. (2007). *Magnetic phases in the kagomé staircase compound studied using powder neutron diffraction*. *Phys. Rev. B*, **75**, 094432.
- Yoo, C.-S., Wei, H., Chen, J.-Y., Shen, G., Chow, P. & Xiao, Y. (2011). *Time- and angle-resolved X-ray diffraction to probe structural and chemical evolution during Al-Ni intermetallic reactions*. *Rev. Sci. Instrum.* **82**, 113901.
- Yusuf, S. M., Jain, A. & Keller, L. (2013). *Field induced incommensurate-to-commensurate magnetic phase transition in $\text{Ca}_3\text{Co}_{1.8}\text{Fe}_{0.2}\text{O}_6$: a neutron diffraction study*. *J. Phys. Condens. Matter*, **25**, 146001.
- Zhang, S. T., Kounga, A. B., Aulbach, E., Ehrenberg, H. & Rödel, J. (2007). *Giant strain in lead-free piezoceramics $\text{Bi}_{0.5}\text{Na}_{0.5}\text{TiO}_3$ - BaTiO_3 - $\text{K}_{0.5}\text{Na}_{0.5}\text{NbO}_3$ system*. *Appl. Phys. Lett.* **91**, 112906.